


Advanced Materials**Accelerator DY 9577**

A LATENT CURING AGENT / ACCELERATOR

GENERAL	Accelerator DY 9577 is a boron trichloride-amine complex, which may be used either as a latent catalytic curing agent for liquid epoxy resins or as a latent accelerator for anhydride cured epoxy resins.	
CHEMICAL DESCRIPTION	Accelerator DY 9577 is a boron trichloride-amine complex.	
APPLICATIONS	Casting Encapsulation Filament winding Pultrusion Molding Electrical tapes	
ADVANTAGES	Exceptional latency at temperatures up to 80°C Highly reactive at temperatures above 120°C Does not degrade electrical properties of cured system Soluble in liquid epoxy resins and hardeners Stabilizes pre-accelerated resins and hardeners	
TYPICAL PROPERTIES*	Visual Appearance	Amber/brown semi-solid
	Melting Point, °C (°F)	26 - 35 (78.8 - 95.0)
	Water Content, %, max	0.1
	Density @ 25°C (77°F), g/cm ³ (lb/gal.)	1.1 (9.2)
	* Typical properties are based on Huntsman's test methods. Copies are available upon request.	
FORMULATIONS	The amount of Accelerator DY 9577 used in any formulation will depend on the resin and hardener used and the reactivity required. In general, when Accelerator DY 9577 is used as a catalytic curing agent, 1 to 5 phr* will suffice. When used as an accelerator for anhydride cured systems, concentration of 0.1 to 1 phr of Accelerator DY 9577 is usually sufficient. The excellent latency at temperatures below 80°C is demonstrated in Figures 1-3. * Parts per 100 parts of resin	

**FORMULATIONS
(CONTINUED)**

**Figure 1 Latency Test
Viscosity vs. Time**

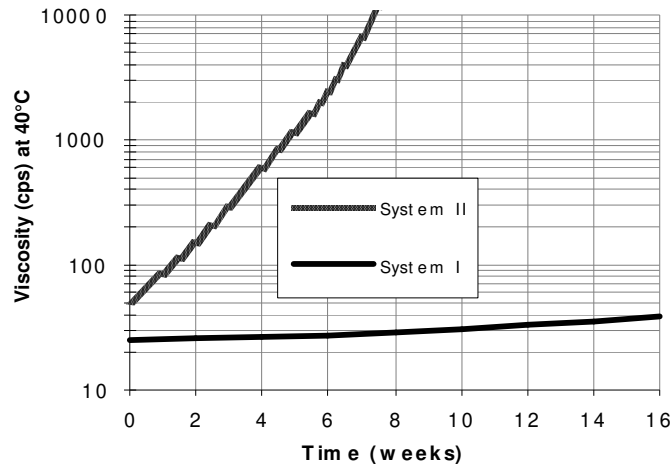


System I

Araldite® GY 6010 100 pbw
Accelerator DY 9577 3 pbw

System II

Araldite® GY 6010 100 pbw
BF₃•MEA 3 pbw


**Figure 2 Latency Test at Various Temperatures
Viscosity vs. Time (one pound mass)**

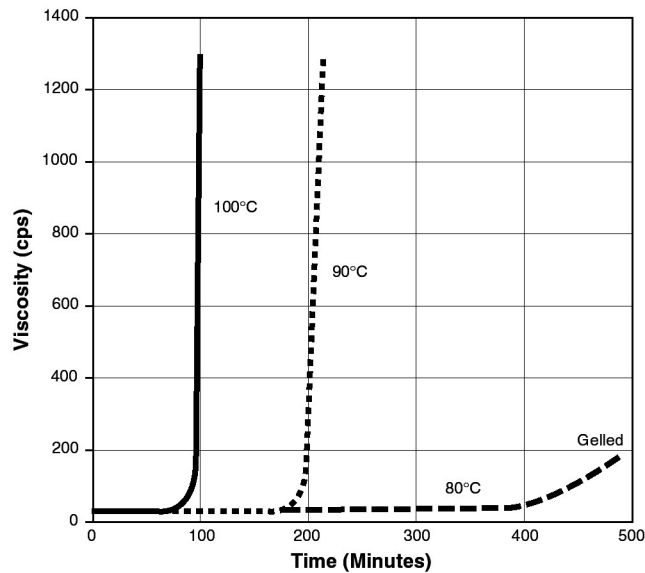

Araldite® GY 6010	100 pbw
Aradur® 907	85 pbw
Accelerator DY 9577	0.5 pbw

**FORMULATIONS
(CONTINUED)**

**Figure 3
30 Gram Gel Time vs. Temperature**

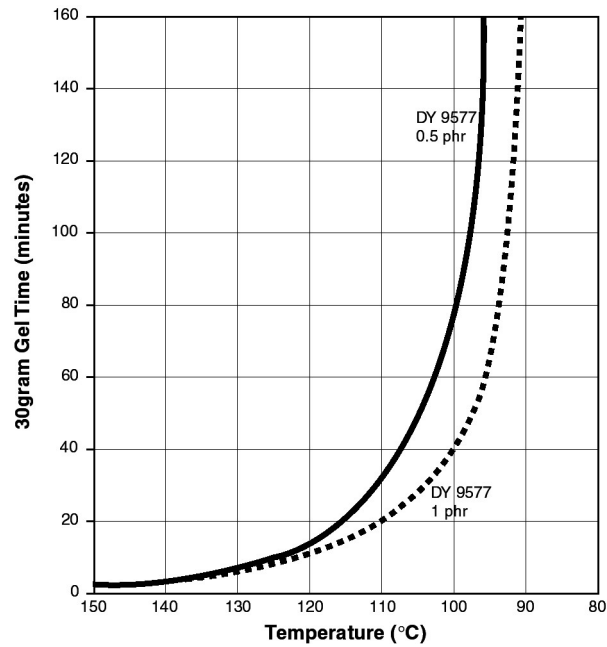

Araldite® CY 184 100 pbw
 Aradur® 907 100 pbw
 Accelerator DY 9577 as indicated

FORMULATION NO.

	1	2	3	4
	Parts by weight			
Araldite® CY 184	100	100	-	-
Araldite® GY 6010	-	-	100	100
Aradur® 907	100	-	85	-
Tetrahydrophthalic anhydride	-	100	-	85
Accelerator DY 9577	0.5	0.5	0.5	0.5

Cure Cycle: Gel @ 120°C + 2 hr cure @ 150°C

Mechanical properties @ 25°C

Tensile strength, psi	12,400	12,300	12,100	12,900
Tensile modulus, psi x 10 ⁵	4.9	4.8	4.3	4.8
Elongation, %	5.4	6.3	5.4	4.9
Flexural strength, psi	19,100	19,900	18,500	21,000
Flexural modulus, psi x 10 ⁵	4.5	4.7	4.3	4.8
Izod impact strength, ft-lb/in	0.2	0.4	0.3	0.3
Heat deflection, °C	103	101	127	110
Water absorption, 2 hr boil, weight gain %	0.5	0.5	0.2	0.4

**FORMULATIONS
(CONTINUED)**

Table 1: Comparison of BF₃ and BCl₃• Amine Complexes

Accelerator DY 9577 is a BCl₃• amine complex, which can be used in place of BF₃• MEA to give improved latency, higher reactivity at 120°C and better electrical properties.

The following formulations display the superior properties of Accelerator DY 9577.

	1	2	3
	Parts by weight		
Araldite® GY 6010	100	100	100
BF ₃ • MEA*	3	-	-
Accelerator DY 9577	-	3	5

Physical Properties

% boron in system	0.28	0.11	0.18
Initial viscosity @ 40°C, cPs	76,000	21,500	18,500
Time to 2x initial visc. @ 40°C, wks	1.0	>15	>8
Gel time (7.5g in oil bath), min @ 90°C	719	608	404
@ 105°C	196	169	83
@ 120°C	63	34	13

**Cure cycle, hours: @
120°C + 150°C + 190°C**

Heat Distortion Temperature,°C

1/2	0	0	-	-	58
3	0	0	-	-	87
8	0	0	-	94	-
16	0	0	88	-	-
2	1	0	98	88	108
2	6	2	156	130	128

Electrical Properties

Cure schedule: 2 hrs @ 120°C + 6 hrs @ 150°C + 2 hrs @ 190°C

Tan 10 ³ @ 50 Hz and 20°C	4	3	4
Temp. for tan = 0.05 @ 50 Hz	123°C	153°C	142°C
Tan 10 ³ @ 1 kHz and 20°C	<5	<5	5
Temp. for tan = 0.05 @ 1 kHz	155°C	177°C	163°C

* Please refer to DT 3357 data sheet for recommended use levels to achieve desired gloss range.

**FORMULATIONS
(CONTINUED)****Laminating Properties
Formulation No.**

1	2
Parts by weight	

Araldite® GY 6005	100	50
Araldite® EPN 1138	-	50
Aradur® 906	80	80
Accelerator DY 9577	1	1

Post cure:	16 hr. @176°C	2 hr. @ 150°C+
		2 hr. @ 176°C

Reinforcement: Fiberite 700P Fabric

Mechanical Properties

Flexural strength, psi		
@ 25°C	148,500	189,000
@ 250°F	113,800	132,100
Flexural modulus, psi x 10 ⁶		
@ 25°C	14.0	12.97
@ 250°F	12.6	12.64
Short beam shear, psi		
@ 25°C	10,500	10,800
@ 250°F	6600	7400

**Powder Coating
Formulation No.**

1	2
Parts by weight	

Araldite® GT 6063	37.70	14.24
Araldite® GT 6450	22.60	34.81
Uralac P 5070 (DSM)	-----	14.31
TiO ₂	29.35	30.00
Matting Agent DT 3357	9.70	6.27
Accelerator DY 9577	0.45	0.17
Benzoin (BASF)	0.20	0.20
Total	100.00	100.00

Coating Properties:

Cure Cycle, min/°C	15/200	15/200
Film thickness, mils	2.0	2.0

Film Properties:

Substrate	0.032" CRS panels	
20° gloss, %	1.3	0.7
60° gloss, %	2.4	4.5
Reverse impact, in-lbs	160	160
Direct impact, in-lbs	160	160
MEK resistance, double rubs	>200	>200

PACKAGING & STORAGE Accelerator DY 9577 is supplied in 40 pound steel drums. It should be stored in sealed containers at temperatures not exceeding 40°C. Containers should be kept closed to prevent moisture absorption and contamination.

HANDLING/SAFETY PRECAUTIONS **Caution! May cause irritation. May be harmful if swallowed or inhaled.**

Avoid contact with eyes, skin or clothing.
Avoid inhaling vapor.
Use with adequate ventilation.
Wash after handling.
Store in cool area in tightly closed containers to prevent contamination and water absorption.

**Read Material Safety Data Sheet Before Using.
For Industrial Use Only.**

FIRST AID

In case of contact:

Eyes: Promptly flush eyes with water for at least 15 minutes.

Skin: Promptly wash with mild soap and water.

Inhalation: Remove to fresh air. Give oxygen if breathing is difficult.

Ingestion: If conscious, give large quantities of water. Call a physician.

IMPORTANT LEGAL NOTICE

Sales of the product described herein ("Product") are subject to the general terms and conditions of sale of either Huntsman Advanced Materials LLC, or its appropriate affiliate including without limitation Huntsman Advanced Materials (Europe) BVBA, Huntsman Advanced Materials Americas Inc., or Huntsman Advanced Materials (Hong Kong) Ltd. ("Huntsman"). The following supercedes Buyer's documents.

Huntsman warrants that at the time and place of delivery all Products sold to Buyer shall conform to the specifications provided to Buyer by Huntsman.

While the information and recommendations included in this publication are, to the best of Huntsman's knowledge, accurate as of the date of publication, NOTHING CONTAINED HEREIN (EXCEPT AS SET FORTH ABOVE REGARDING CONFORMANCE WITH SPECIFICATIONS PROVIDED TO BUYER BY HUNTSMAN) IS TO BE CONSTRUED AS A REPRESENTATION OR WARRANTY OF ANY KIND, EXPRESS OR IMPLIED, INCLUDING BUT NOT LIMITED TO ANY WARRANTY OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE, NONINFRINGEMENT OF ANY INTELLECTUAL PROPERTY RIGHTS, OR WARRANTIES AS TO QUALITY OR CORRESPONDENCE WITH PRIOR DESCRIPTION OR SAMPLE, AND THE BUYER ASSUMES ALL RISK AND LIABILITY WHATSOEVER RESULTING FROM THE USE OF SUCH PRODUCT, WHETHER USED SINGLY OR IN COMBINATION WITH OTHER SUBSTANCES.

No statements or recommendations made herein are to be construed as a representation about the suitability of any Product for the particular application of Buyer or user or as an inducement to infringe any patent or other intellectual property right. Buyer is responsible to determine the applicability of such information and recommendations and the suitability of any Product for its own particular purpose, and to ensure that its intended use of the Product does not infringe any intellectual property rights.

The Product may be or become hazardous. The Buyer should obtain Material Safety Data Sheets and Technical Data Sheets from Huntsman containing detailed information on Product hazards and toxicity, together with proper

shipping, handling and storage procedures for the Product, and should comply with all applicable governmental laws, regulations and standards relating to the handling, use, storage, distribution and disposal of, and exposure to the Product. Buyer shall also take all steps necessary to adequately inform, warn and familiarize its employees, agents, direct and indirect customers and contractors who may handle or be exposed to the Product of all hazards pertaining to and proper procedures for safe handling, use, storage, transportation and disposal of and exposure to the Product, and the containers or equipment in which the Product may be handled, shipped or stored.

Araldite and Aradur are registered trademarks of Huntsman LLC or an affiliate thereof in one or more countries, but not all countries.

© 2006 Huntsman Advanced Materials Americas Inc.

Main Offices :

Huntsman Corporation

10003 Woodloch Forest Dr.
The Woodlands
Texas 77380
(281) 719-6000

**Huntsman Advanced Technology
Center**

8600 Gosling Rd.
The Woodlands
Texas 77381
(281) 719-7400