

Advanced Materials**Araldite® GY 6010**

A MEDIUM VISCOSITY, UNMODIFIED LIQUID EPOXY RESIN

GENERAL	Araldite® GY 6010 is a general purpose unmodified liquid epoxy resin applied widely in both room temperature and heat cured systems. It is the standard from which a great number of variations were developed.
----------------	---

CHEMICAL DESCRIPTION	Araldite® GY 6010 is an unmodified liquid epoxy resin based on bisphenol A and epichlorohydrin.
-----------------------------	---

APPLICATIONS	Coatings Electrical Civil Engineering	Matrix Adhesives
---------------------	---	---------------------


ADVANTAGES	Superior mechanical and electrical properties Excellent chemical resistance Good heat resistance Excellent adhesion Outstanding versatility Easy to cure with a variety of different type hardeners Compatible with many different fillers, diluents and accelerators Conforms to FDA listings in 21 CFR 175.300
-------------------	---

TYPICAL PROPERTIES*	Visual Appearance	Clear, no contamination
	Color, Gardner, max	1
	Epoxy Value, eq./kg	5.2 - 5.5
	Epoxy Equivalent, g/eq.	182 - 192
	Viscosity @ 25°C (77°F), mPa s (cPs)	11,000 - 13,000
	Density @ 25°C (77°F), g/cm ³ (lb/gal.)	1.15 - 1.18 (9.6 - 9.8)
	Flash Point, Closed Cup, °C (°F)	254 (490)

* Typical properties are based on Huntsman's test methods. Copies are available upon request.

**REDUCING VISCOSITY OF
Araldite® GY 6010**

The graph below represents the viscosity of modified Araldite® GY 6010 vs % diluent (by weight) for five reactive diluents.

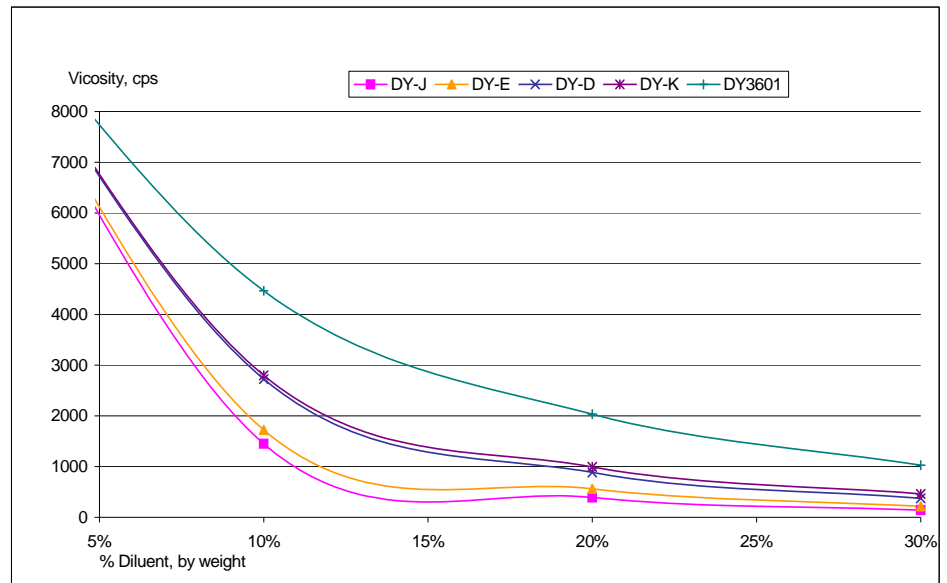

The addition of reactive diluents to Araldite® GY 6010 influences wet properties of coatings and performance of the cured films. Depending on the diluent used, it is expected that:

- 1) The viscosity and the reactivity of the system will be reduced.
- 2) Mechanical properties of the cured system will be impaired.
- 3) Thermal stability of the system will be reduced.
- 4) Resistance to water and aqueous solutions at elevated temperatures will be reduced.
- 5) Resistance to acids and organic solvents at ambient temperatures will be reduced.

The extent to which the above properties are affected depends on the reactive diluent content and its chemical nature.

HARDENERS

The final properties of a cured Araldite® GY 6010 system at ambient temperature depend, to a great extent, on the hardener selection. Because of its versatility, Araldite® GY 6010 can be cured with most types of hardeners such as:

Type	Huntsman Aradur®	Mixing Ratio phr*	Pot Life 100g mass @ 25°C (77°F) Hrs:Min
Modified Aliphatic amines	Aradur® 956	25	0:35
	Aradur® 943	20	0:15
	Aradur® 3440	35-45	0:35
	Aradur® 3441	60-80	0:75
Cycloaliphatic amines	Aradur® 2964	50	0:35
	Aradur® 2963	45	0:45
	Aradur® 1341	60	0:25
	Aradur® 265	50	0:40
	Aradur® 355	26	0:30
	Aradur® 847	40	0:40
Polyamides	Aradur® 115-2	35+	10:00
	Aradur® 125-2	35+	6:30
	Aradur® 140-2	35+	3:30
	Aradur® 283	70	2:30
	Aradur® 360	60	7:30
Anhydrides	Aradur® 906 NMA	80-90	-
	Aradur® 917 MTHPA	80-90	-

*per hundred parts by weight resin

+Depending on desired properties it can be 35-100 phr

CURING TIME The curing time depends on the hardener used, the temperature applied and the mass of the resin/hardener mix. We recommend the following cure schedules for achieving the optimum properties of Araldite® GY 6010 systems.

Aradur® 906*	2 hr @ 10°C (212°F) +2-4 hr @150-200°C (302-398°F)
TETA Hardener	7 days @ room temperature or 24 hr @ 40°C or 2-9 hr @ 100°C (212°F)
Aradur® 956	7 days @ room temperature or 24 hr @ 40°C (104°F) or 2-8 @ 100°C (212°F)
Aradur® 125-2	7 days @ room temperature or 2-8 hr @ 100°C (212°F)
Aradur® 976-1	Gel @ 120-150°C (248-302°F) + 2-4 hr @ 175-200°C (347-392°F)

* Accelerators such as Accelerator 960-1, DY 062 (benzyl dimethyl amine), etc., are usually used with Aradur® 906.

FORMULATIONS	Product	Parts by weight
	Araldite® GY 6010	100
	Aradur® 2964	50
	Physical Properties	
	Viscosity mixed @25°C, cPs	1000
	Gel time, min., @25°C	30
	Dust dry time, hr, @25°C	4
	Full-cure time, hr, @25°C	7
	Flow @25°C	Very good
	Transparency	Clear
	Surface appearance	Smooth, glossy
	Exudation	None
	Impact test	
	2 months @ 20°C (68°F), in/lb	70
	2 months @ 60°C (140°F), in/lb	70
	Mandrel test	15mm mandrel
	2 months @ 20°C (68°F)	180°
	2 months @ 60°C (140°F)	60°
	Boiling water test 6 hr @ 96°C (205°F)	
	Adhesion on sandblasted mild steel sheet	Unchanged
	After curing @ 20°C (68°F)/100% RH	
	Full-time cure, hrs.	Approx. 30
	Surface appearance	Smooth, glossy
	Transparency	Clear
	Exudation	None

FORMULATIONS (CONTINUED)	Chemical Resistance						Test time, Months							
	¼	½	1	2	3	4	5	6	7	8	9	10	11	12
Water, deionized	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Seawater, synthetic	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Sulfuric acid, 10%	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Sulfuric acid, 30%	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Sulfuric acid, 70%	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Hydrochloric acid, 10%	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Hydrochloric acid, 20%	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Hydrochloric acid, 36%	+	+	+	+	A	D								
Acetic acid, 5%	+	+	+	+	D									
Acetic acid, 10%	+	A	D											
Ammonia, 10%	+	+	+	+	+	+	A	A	A	A	A	D		
Ammonia, 25%	+	+	A	D										
Caustic soda, 20%	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Acetone	D													
Butanol	D													
Butyl acetate	+	+	+	+	+	+	+	+	+	+	+	+	+	(+)
Diacetone alcohol	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Ethyl glycol	A	A	A	A	A	A	A	A	A	A	A	D		
Ethanol, 50%	+	+	+	A	A	A	A	A	A	A	A	A	A	A
Ethanol, 96%	D													
Octanol	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Xylene	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Toluene	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Benzene	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Trichloroethylene	+	+	+	+	+	+	+	+	+	+	+	+	+	+
Crude oil	+	+	+	+	+	+	+	+	+	+	+	+	+	+

(+) = slight softening initially but regenerate very rapidly

+ = resistant

A = attacked

D = destroyed Hot Curing Casting Applications

Systems containing GY 6010 and polyamide hardeners such as Aradur[®] 939 reacting rapidly at relatively moderate temperatures (e.g., 5 min @ 100°C), provide excellent properties after curing at 150°C. Table 1 provides information on the effect of cure times on Adhesive Tensile Shear Strength.

The mixing ratio of Aradur[®] 939 is not critical and can be varied. As might be expected, the physical properties are dependent on the amount of hardener that is used. Table 2 illustrates several variations in the mix ratio.

Product	Parts by weight
Araldite [®] GY 6010	100
Aradur [®] 939	35
Physical Properties	
Viscosity of mixture @ 25°C, cPs	120,000
Gel time (1g on cure plate), sec	
@ 100°C	300
@ 121°C	124
@ 150°C	54

FORMULATIONS

(CONTINUED)

Cure schedule: Gel @ 90°C + 3 hrs @ 150°C

Mechanical Properties @ 25°C (ultimate)

Heat deflection temperature, °C	97
Tensile strength, psi	11,500
Elongation, %	4.6
Tensile modulus, psi x 10 ⁵	4.9
Weight loss after 48 hrs @ 200°C,%	2.0

Electrical Properties

Volume resistivity (ohm-cm)	
@ 25°C	1.1 x 10 ¹⁶
@ 100°C	9.0 x 10 ¹²
@ 150°C	1.3 x 10 ⁹

Table 1: Effect of Cure Time/Temp. on Adhesive Tensile Shear Strength

	Parts by Weight	
Araldite® GY 6010	100	
Aradur® 939	35	
Cure: 6.5 min @ 150°C		
Tensile shear strength, psi		
@ 25°C	1620	
@ 82°C	1050	
@ 149°C	100	
Cure: 10 min @ 159°C		
Tensile shear strength, psi		
@ 25°C	1630	
@ 82°C	1050	
Tensile shear strength (psi)	Tested @	
Cure: 10 min @:	25°C	82°C
100°C	560	-
121°C	560	880
150°C	1560	1050
177°C	1630	820

Table 2: Effect of Mix Ratio on Physical/Mechanical Properties

Aradur® 939 (phr) with Araldite® GY 6010	Gel time @ 150°C, sec	HDT, °C	Tensile Shear Strength @ 25°C, psi
25	76	78	1270
30	58	90	-
35	54	97	1620
40	45	95	1480
45	41	90	1690

FDA STATUS	Araldite [®] GY 6010 is included in Section 175.300 of Title 21 of the Code of Federal Regulations (21 CFR 175.300) for resinous and polymeric coatings.
PACKAGING & STORAGE	Araldite [®] GY 6010 is supplied in bulk and in 500 pound steel drums. This product has a minimum shelf life of four years when stored in unopened sealed containers in a dry location at room temperature. Like most liquid epoxy resins, Araldite [®] GY 6010 may crystallize when stored below room temperature. Heating the resin to 60-70°C (140-160°F), preferably in a water bath, for several hours, will reliquify it and restore its original properties.
HANDLING/SAFETY PRECAUTIONS	<p>Warning : Causes irritation. May cause allergic skin reaction.</p> <p>Avoid contact with eyes, skin or clothing. Avoid breathing vapor, mist or spray. Use with adequate ventilation. Promptly remove wet, contaminated clothing and wash before reuse. Wash after handling. Store in a cool, dry area in closed containers.</p> <p>Read Material Safety Data Sheet Before Using. For Industrial Use Only.</p>
FIRST AID	<p>In case of contact :</p> <p>Eyes : Immediately flush with water for at least 15 minutes. Call a physician.</p> <p>Skin : Promptly wash thoroughly with mild soap and water.</p> <p>Inhalation : Remove to fresh air. Give oxygen if breathing is difficult.</p> <p>Ingestion : If conscious, give plenty of water. Get medical attention.</p>

IMPORTANT LEGAL NOTICE

Sales of the product described herein ("Product") are subject to the general terms and conditions of sale of either Huntsman Advanced Materials LLC, or its appropriate affiliate including without limitation Huntsman Advanced Materials (Europe) BVBA, Huntsman Advanced Materials Americas Inc., or Huntsman Advanced Materials (Hong Kong) Ltd. ("Huntsman"). The following supercedes Buyer's documents.

Huntsman warrants that at the time and place of delivery all Products sold to Buyer shall conform to the specifications provided to Buyer by Huntsman.

While the information and recommendations included in this publication are, to the best of Huntsman's knowledge, accurate as of the date of publication, NOTHING CONTAINED HEREIN (EXCEPT AS SET FORTH ABOVE REGARDING CONFORMANCE WITH SPECIFICATIONS PROVIDED TO BUYER BY HUNTSMAN) IS TO BE CONSTRUED AS A REPRESENTATION OR WARRANTY OF ANY KIND, EXPRESS OR IMPLIED, INCLUDING BUT NOT LIMITED TO ANY WARRANTY OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE, NONINFRINGEMENT OF ANY INTELLECTUAL PROPERTY RIGHTS, OR WARRANTIES AS TO QUALITY OR CORRESPONDENCE WITH PRIOR DESCRIPTION OR SAMPLE, AND THE BUYER ASSUMES

ALL RISK AND LIABILITY WHATSOEVER RESULTING FROM THE USE OF SUCH PRODUCT, WHETHER USED SINGLY OR IN COMBINATION WITH OTHER SUBSTANCES.

No statements or recommendations made herein are to be construed as a representation about the suitability of any Product for the particular application of Buyer or user or as an inducement to infringe any patent or other intellectual property right. Buyer is responsible to determine the applicability of such information and recommendations and the suitability of any Product for its own particular purpose, and to ensure that its intended use of the Product does not infringe any intellectual property rights.

The Product may be or become hazardous. The Buyer should obtain Material Safety Data Sheets and Technical Data Sheets from Huntsman containing detailed information on Product hazards and toxicity, together with proper shipping, handling and storage procedures for the Product, and should comply with all applicable governmental laws, regulations and standards relating to the handling, use, storage, distribution and disposal of, and exposure to the Product. Buyer shall also take all steps necessary to adequately inform, warn and familiarize its employees, agents, direct and indirect customers and contractors who may handle or be exposed to the Product of all hazards pertaining to and proper procedures for safe handling, use, storage, transportation and disposal of and exposure to the Product, and the containers or equipment in which the Product may be handled, shipped or stored.

Araldite and Aradur are registered trademarks of Huntsman LLC or an affiliate thereof in one or more countries, but not all countries.

© 2006 Huntsman Advanced Materials Americas Inc.

Main Offices :

Huntsman Corporation
10003 Woodloch Forest Dr.
The Woodlands
Texas 77380
(281) 719-6000

**Huntsman Advanced Technology
Center**
8600 Gosling Rd.
The Woodlands
Texas 77381
(281) 719-7400